



**Calhoun: The NPS Institutional Archive**  
**DSpace Repository**

---

Theses and Dissertations

1. Thesis and Dissertation Collection, all items

---

1954

A study of the effect of variations of  
concentration and surface treatment on  
adsorption in a metallic copper-iodide ion system

Lynn, George Anthony

Monterey, California: U.S. Naval Postgraduate School

---

<http://hdl.handle.net/10945/14650>

---

*Downloaded from NPS Archive: Calhoun*



Calhoun is the Naval Postgraduate School's public access digital repository for research materials and institutional publications created by the NPS community. Calhoun is named for Professor of Mathematics Guy K. Calhoun, NPS's first appointed -- and published -- scholarly author.

**Dudley Knox Library / Naval Postgraduate School**  
**411 Dyer Road / 1 University Circle**  
**Monterey, California USA 93943**

<http://www.nps.edu/library>

A STUDY OF THE EFFECTS OF VARIATIONS OF  
CONCENTRATION AND SURFACE TREATMENT ON  
ADSORPTION IN A METALLIC COPPER-IODIDE ION SYSTEM

GEORGE ANTHONY LYNN

Library  
U. S. Naval Postgraduate School  
Monterey, California





# Artisan Gold Lettering & Smith Bindery

593 - 15th Street

Oakland, Calif.

Glencourt 1-9827

## DIRECTIONS FOR BINDING

### BIND IN

(CIRCLE ONE)

### BUCKRAM

COLOR NO. 8854

### FABRIKOID

COLOR                     

### LEATHER

COLOR                     

### OTHER INSTRUCTIONS

Letter in gold.

Letter on the front cover:

A STUDY OF THE EFFECTS OF VARIATIONS OF  
CONCENTRATION AND SURFACE TREATMENT ON  
ADSORPTION IN A METALLIC COPPER-IODIDE  
ION SYSTEM

GEORGE ANTHONY LYNN

LETTERING ON <sup>shelf</sup> BACK  
TO BE EXACTLY AS  
PRINTED HERE.

LYNN

1954

Thesis  
L99



A STUDY OF THE EFFECTS OF VARIATIONS OF CONCENTRATION AND SURFACE  
TREATMENT ON ADSORPTION IN A METALLIC COPPER-IODIDE ION SYSTEM

\* \* \* \* \*

George A. Lynn





A STUDY OF THE EFFECT OF VARIATIONS OF CONCENTRATION AND SURFACE  
TREATMENT ON ADSORPTION IN A METALLIC COPPER-IODIDE ION SYSTEM

by

George Anthony Lynn

Captain, United States Army

Submitted in partial fulfillment  
of the requirements  
for the degree of  
MASTER OF SCIENCE  
IN  
PHYSICS

United States Naval Postgraduate School  
Monterey, California

1 9 5 4

Thesis  
L 99

This work is accepted as fulfilling  
the thesis requirements for the degree of

MASTER OF SCIENCE

IN

PHYSICS

from the

United States Naval Postgraduate School



## PREFACE

This study was conducted at the United States Naval Postgraduate School in Monterey, California, during the spring of 1954 in partial fulfillment of the requirements for the degree of Master of Science in Physics.

The author wishes to express his appreciation to Professors Gilbert F. Kinney and William W. Hawes for their assistance, cooperation, and guidance in the preparation of this paper.



## TABLE OF CONTENTS

|   | Page  |
|---|-------|
| Introduction                                  | 1-6   |
|   |       |
| Part I  |       |
| Definition of Adsorption.....                 | 1     |
| Classification of Adsorption Processes.....   | 1     |
| Surface Factors.....                          | 2     |
|   |       |
| Part II                                       |       |
| Factors Important in This Study.....          | 4     |
| Review of Recent Reports.....                 | 4     |
| Purpose of This Study.....                    | 5     |
| Summary of Results.....                       | 5     |
|   |       |
| Experimental Procedure                        | 7-10  |
|   |       |
| Method of Approach and Basic Assumptions..... | 7     |
| Choice of Active Material.....                | 7     |
| Choice of Adsorbent.....                      | 8     |
| Technique and Measurements.....               | 8     |
| Surface Treatment.....                        | 9     |
| Activity Losses.....                          | 10    |
|   |       |
| Experimental Results                          | 11-23 |
|   |       |
| Amount of Adsorption.....                     | 11    |
| Two-Phase System.....                         | 16    |
| Surface Effects.....                          | 17    |
| Rate of Adsorption.....                       | 21    |
| Summary and Conclusions.....                  | 21    |
|   |       |
| Appendix                                      |       |
|   |       |
| Bibliography                                  |       |
| Data Sheets, Series 1-6                       |       |





# LIST OF GRAPHS AND ILLUSTRATIONS

|   | Page |
|---|------|
| Graph I-1, Log Activity vs Reciprocal Time, Series 1. . . . .   | 12   |
| Graph I-2, Log Activity vs Reciprocal Time, Series 2. . . . .   | 13   |
| Graph I-3, Log Activity vs Reciprocal Time, Series 6. . . . .   | 14   |
| Graph I-4, Log Activity vs Reciprocal Time, Series 3. . . . .   | 15   |
| Graph II, Illustration of Surface Effects, Series 4 and 5 . . . | 18   |
| Graph III, Illustration of Surface Effects, Series 3. . . . .   | 19   |
| Radio-autographs, Planchets 1-4, Series 2 . . . . .             | 20   |
| Graph IV, Rate of Adsorption vs Time. . . . .                   | 22   |



## INTRODUCTION

### Part I

Adsorption has been defined<sup>1</sup> as the tendency of a solid to condense upon its surface a layer of any gas or solute with which it may be in contact. The amount of material adsorbed may vary depending upon such factors as temperature, concentration or pressure of the adsorptive, condition of the surface of the adsorbent, and the physical and chemical properties of the adsorbent and the adsorptive. A more general definition<sup>2</sup> states that a substance is adsorbed if the concentration of the substance in a boundary region is higher than in the interior of the system. The definition of adsorption rests on measurements of concentration, and carries no implication of mechanism.

Adsorption takes place at the interface between adjacent phases, and the interface may be solid-liquid, solid-gas (or vapor), liquid-liquid, or liquid-gas (or vapor). In a reversible process, the molecules can return to the phase from which they came, their place being taken by other molecules; and at equilibrium, the rate of departure equals the rate of arrival of the molecules at the interface.

All adsorptive processes are exothermic, and the decrease in the heat content of the system is called the heat of adsorption. Adsorption at solid surfaces may be either physical (van der Waals) or chemical, according to the magnitude of the energy change involved. There is no rigid distinction, however, as adsorptive processes may involve

1. F. H. Getman and F. Daniels, *Outlines of Physical Chemistry*. John Wiley and Sons, New York, 1940, p 255.

2. H. G. Cassidy, *Adsorption and Chromatography*. Interscience Press, New York, 1951, p 1.



energy changes ranging from relatively small in physical adsorption to the order of magnitude of those found in chemical reactions in chemical adsorption. In intermediate ranges, the process may be thought of as involving both physical and chemical adsorption simultaneously, although this has not been clearly shown.

A third classification of adsorption, activated adsorption, has been described by Adam.<sup>3</sup> Activated adsorption takes place slowly and at about room temperature. Here it is postulated that in order for adsorption to take place, some sort of potential barrier must be overcome by the molecules, so that only those with sufficient energy can be adsorbed. At room temperature, the energy distribution may be such that only a relatively few molecules possess sufficient energy to surmount the barrier, and in such situations an increase in temperature would increase the rate of adsorption.

When adsorption occurs from a mixture of substances, as from a solution, there will be considerable competition for the interface. It is here that the geometry of the surface and the molecules of the adsorptive are of great importance, as well as the physical and chemical properties of the substances.

The adsorbent introduces many factors which might have an influence on the adsorptive process. The physical composition of the surface will certainly have an effect on adsorption.<sup>4</sup> Langmuir has shown that on a plane, crystalline, chemically homogeneous surface the disposal of sites on which adsorption can take place will be in a regular pattern. Any irregularities in the pattern lead to the formation of so-called "active

3. N. K. Adam, *The Physics and Chemistry of Surfaces*, 3rd Ed. Oxford University Press, London, 1941, p 252.

4. Cassidy, *op. cit.*, p 43 ff.





centers". On an amorphous surface regularity may or may not exist. The spaces available on a plane crystal may be of several kinds, but the regularity of the surface may lead to some stoichiometric relation in the adsorption of different substances. At the edges and corners of an adsorbent certain molecules will be in a somewhat more exposed position. Such molecules might be more active in adsorption than others.

If the surface is rough, then more of the surface molecules will be in an exposed position, and the roughness might therefore be more conducive to increased adsorption of small molecules per unit number of surface molecules over the plane surface, while with large molecules the effect might be opposite. If the surface contains capillaries and fissures, adsorption may be favored for those small molecules which can enter these imperfections in the surface, while larger molecules may therefore have large areas of the surface excluded to them for the purpose of adsorption.

Smooth surfaces are extremely difficult to obtain. Frazer, Patrick, and H. E. Smith<sup>5</sup> observed that on glass surfaces which had never been in contact with liquids, the adsorbed layer was probably one molecule thick, whereas on glass that had been etched by contact with liquids the adsorbed layer was probably several molecules thick. It is possible that some surface imperfections can have a negligible effect, since at the interface mutual interaction between adsorbed molecules may cause them to adhere laterally and so influence the quantity adsorbed by allowing the adsorbed film to bridge roughness and fissures in the adsorbent.

5. Frazer, Patrick, and H. E. Smith, J Phys Chem, 31, 897 (1927).





## Part II

In the case with which this study is concerned, that of a solid-solution type of interface, there are several features which must be considered. The liquid is homogeneous, due to the thermal motions of its particles. The solid surface, on the other hand, is very likely to be non-homogeneous, resulting in effects which will be discussed more fully later in this paper. We also have to consider that both the solvent and the solute molecules will have a tendency to be adsorbed, the effect here being dependent upon the nature of the solvent and the solute, with particular reference to the possibility of interaction, dissociation, or incompatibility. Since in this study extremely low concentrations of solute are employed, errors due to adsorption of the solvent are expected to be negligible, since there is a tendency toward preferential adsorption of the component present in the smaller concentration. Furthermore, it is not expected that effects due to interaction, dissociation, or incompatibility will affect the qualitative significance of the results.

In general, the recent literature is relatively sparse insofar as work on the rate of adsorption at solid-solution interfaces is concerned. There has been a considerable amount of work reported on gas adsorption on solids, and it is to be expected that this process should be in some way related to adsorption from solutions. An example of this work is the report by Russell and Stokes<sup>6</sup> of their study of the adsorption of hydrogen on alumina. They report a very high initial adsorption rate followed by a sharp drop to lower rates. In work with solutions,

6. A. S. Russell and J. J. Stokes, Jr., J. Am Chem Soc, 69, 1316 (1947).



Zettlemoyer and co-workers<sup>7</sup> have reported on the adsorption of fluoride from aqueous solutions, their results similarly showing a high initial rate followed by a sharp change to lower rates. Some recent work employing radioactive isotopes has been reported by King and Schochet.<sup>8</sup> They studied the adsorption of silver salts on silver using  $\text{Ag}^{110}$  as a tracer, and their findings followed the pattern described above. In addition, they reported that treating the silver with dilute nitric acid prior to use resulted in an increase in the amount of  $\text{Ag}^{110}$  adsorbed. Rydberg and Rydberg<sup>9</sup> have reported on the adsorption on glass and polyethylene of  $\text{Th}^{232}$ , present in solution in tracer concentrations. They found a very high initial rate of adsorption (half time 15-25 minutes) and a very slow rate after about one hour (half time 7 hours). They also noted a sharp adsorption maximum on glass around pH 4.2.

The purpose of this study is twofold. First, it is to observe the effect of changes in the concentration of the solution on the rate of adsorption and on the total amount of substance adsorbed, and to observe the effects of surface imperfections on the overall pattern of adsorption. The second is to lay the groundwork for future research in this field at this institution by devising basic techniques which can be adapted to the many phases of this particular field.

In this study, radioactive iodine in very low (tracer) concentrations was the adsorptive, and metallic copper in the form of thin disks was the adsorbent. Results indicate that in general, the overall

7. A. C. Zettlemoyer, E. A. Zettlemoyer, and W. C. Walker, Jr., J Am Chem Soc, 69, 1312 (1947).

8. King and Schochet, J Phys Chem, 57, 895-8 (1953).

9. Rydberg and Rydberg, Svensk Kem Tidskr, 64, 200-11 (1952).



adsorption process can be broken down into two steps or phases whose combined effect is observed. Surface imperfections and variations in preparatory treatment exert a strong influence on the adsorption processes, and may be capable of overriding concentration effects. The total amount of iodide adsorbed varied directly with concentration, except in those cases where surface effects appeared to exert severe inhibitions on the adsorption process. The rate of adsorption was initially high, and fell rapidly to low values within a few hours at most, following closely the pattern observed by others.





## Experimental Procedure

Many experiments on adsorption employ the technique of measuring the concentration of the adsorptive before and after the adsorbent has been permitted to perform its function, with the difference being considered adsorbed. With the current availability of numerous radioactive isotopes, a more direct method of studying adsorption phenomena is provided. It is necessary to make one basic assumption when using radioactive isotopes in the study of adsorption: it is assumed that an active molecule or atom will act in the same manner as an ordinary molecule or atom. Insofar as the phenomenon of adsorption is concerned, the writer feels that this assumption is indeed a valid one. Certainly the active isotope will react chemically in the same manner as an isotope which is not active, and while it may possess additional energy which can be manifested in the release of some form of radiation, this energy does not normally affect its physical properties.

Using this assumption as a basis, we further postulate that the amount of activity on a solid adsorbent which has been immersed in an active solution will be proportional to the amount of adsorptive present. By immersing the adsorbent for varying periods of time, and measuring its activity between immersions, a picture of the activity (and consequently the amount adsorbed) as a function of time is presented. From such a picture, it is relatively simple to differentiate the curve and so determine the rate of adsorption as a function of time.

In deciding on the isotope to be used in this study, consideration was given to several desirable characteristics. First, the isotope should be readily available and comparatively inexpensive. The reasons for this are obvious. Second, the isotope should have a fairly short half-life--





perhaps no longer than two or three weeks, but no shorter than two or three days. The upper limit on the length of half-life comes about from the viewpoint of laboratory contamination, in that an accident with such an isotope will not prevent the use of the laboratory for long periods of time. This is especially important where the facilities must be available for several groups concurrently. Use of shorter half-life materials than the lower limit proposed will result in too rapid decay of the solution, which would be somewhat of a handicap in long test runs. Third, in order to avoid the necessity for elaborate precautions in handling the active solutions and solid adsorbents, it would seem advisable to choose an isotope with relatively low energy radiation, with beta radiation preferable to gamma.

Based on the above considerations, the isotope  $I^{131}$  was chosen. It has an 8-day half-life and emits beta radiation of about 0.6 Mev.

As the solid adsorbent, metallic copper was chosen since it is readily available in a relatively pure state. Further, it etches easily, thus making it easier to obtain uniformity of surface without elaborate pre-treatment. The copper used in this study was prepared in the form of thin disks or planchets of a convenient size.

The actual technique of immersing the copper planchets into the aqueous solution of iodide may be described as follows. A small hole was drilled in each planchet, and a piece of copper wire hooked into it. This provided an easy means of removing the planchet after it had been immersed for the desired time. The planchet was then rinsed lightly to remove any droplets of solution, after which the planchet was dried with a tissue and placed in a holder for counting. Tests were made to



ascertain whether or not the activity on the reverse side would affect the count from the side facing the tube. It was found that the thickness of the planchet was sufficient to shield out completely the radiation from the under side, thus eliminating this as a factor. It should be mentioned here that since any given test run took place over an extended period of time--in some cases as much as a week--it was necessary to correct all counts for decay back to the starting date in order to affect a normalization of the data. By so correcting the data which might be obtained a few days after the initial readings, the atoms or molecules which had been adsorbed and then undergone decay before a count could be taken were effectively included. This obviously must be done, or a considerable amount of adsorptive will go undetected.

The activity of the planchets was determined with the customary setup of a Geiger-Mueller tube in conjunction with an automatic scaler. The tube employed was a Tracerlab TGC-1 type end-window counter. The scaler was a CP-37UD Radio Computer-Indicator also manufactured by Tracerlab. The radioactive iodine was purchased as needed from Tracerlab. The tube was carefully calibrated to determine its characteristics and efficiency factors, so that when determining the concentration of the solutions it could be done on an absolute basis as of the time of measurement. Geometry was fixed by means of a standard holder, which provided a choice of several counting positions.

The surface of the planchets was examined under a low-power microscope, and in general the surface was found to contain many imperfections. These included minute cracks and fissures, as well as small pits and gouges. Many of these were not visible to the unaided eye.





In addition, the surfaces were often dirty. In order to clean up the surfaces and attempt to minimize the effect of the imperfections, the planchets were treated for three minutes in a bath of dilute nitric acid, after which they were rinsed in water to remove excess acid. In one case, the planchets were so prepared and then stored under water for five days prior to use. The effect of this treatment, as opposed to the usual treatment of immediate use after preparation, is discussed with other experimental results. The action of the acid bath removed surface dirt and had some effect in smoothing out pits and gouges. The fissures and cracks were not noticeably affected, insofar as visual examination could determine.

In order to determine if excessive activity losses were occurring during the course of a test run, the concentration of the solution was measured before and after a test run, the latter figure being corrected for decay. In all cases, a small amount of activity was lost, and in accounting for the loss part of it could be traced to the amount of active material adsorbed as measured by the activity on the planchets. The rest of the loss was presumed to have occurred in the process of rinsing solution droplets off the planchets prior to taking a count, and also in adsorption into the glass surfaces of the beaker, stirring rod, and thermometer. In no case was the entire amount lost excessive.



## Experimental Results

The total adsorption pattern was normal. It was expected that the total amount of iodide adsorbed would be greater at the higher concentrations than at the lower ones, but that the percent adsorbed would be greatest at the lowest concentration. Table I illustrates these results, with the figures for total adsorption representing one side of the planchet only. This gives a qualitative picture, which is sufficient for the purpose of this study.

| Concentration                   | Table I                   |                     |            |
|---------------------------------|---------------------------|---------------------|------------|
|                                 | Adsorption after 27 hours |                     |            |
|                                 | Total Activity            | Total Adsorbed      | % Adsorbed |
| .283 $\mu\text{c/ml}$ (300 ml)  | 84.9 $\mu\text{c}$        | 0.88 $\mu\text{c}$  | 1.04%      |
| .096 $\mu\text{c/ml}$ (500 ml)  | 48.0 $\mu\text{c}$        | 0.58 $\mu\text{c}$  | 1.21%      |
| .0325 $\mu\text{c/ml}$ (225 ml) | 7.31 $\mu\text{c}$        | 0.116 $\mu\text{c}$ | 1.59%      |

Not included in this table are the figures for test runs 4 and 5, since in these runs the amount of activity present on the planchets was low due to surface effects. These surface effects will be discussed later in this section.

The log activity- $1/t$  plots of the test runs are presented in two groups, of which the second will be discussed under surface effects. The first group, including runs 1,2,3, and 6, shows the general picture of the adsorption isotherm, which can be represented by an equation of the form  $\alpha = Ae^{-a/t} + Be^{-b/t}$ . The particular equations calculated for each of these runs are as follows:

$$\begin{aligned}\alpha &= 1700 e^{-.102/t} + 18000 e^{-2.16/t} && (.283 \mu\text{c/ml concentration}) \\ \alpha &= 3900 e^{-.172/t} + 7400 e^{-1.05/t} && (.096 \mu\text{c/ml concentration}) \\ \alpha &= 1100 e^{-.070/t} + 1500 e^{-2.18/t} && (.088 \mu\text{c/ml concentration}) \\ \alpha &= 850 e^{-.075/t} + 2200 e^{-2.08/t} && (.0325 \mu\text{c/ml concentration})\end{aligned}$$






I-1

$$\ln a - 1/t$$

$$.283 \text{ sec/nl}$$

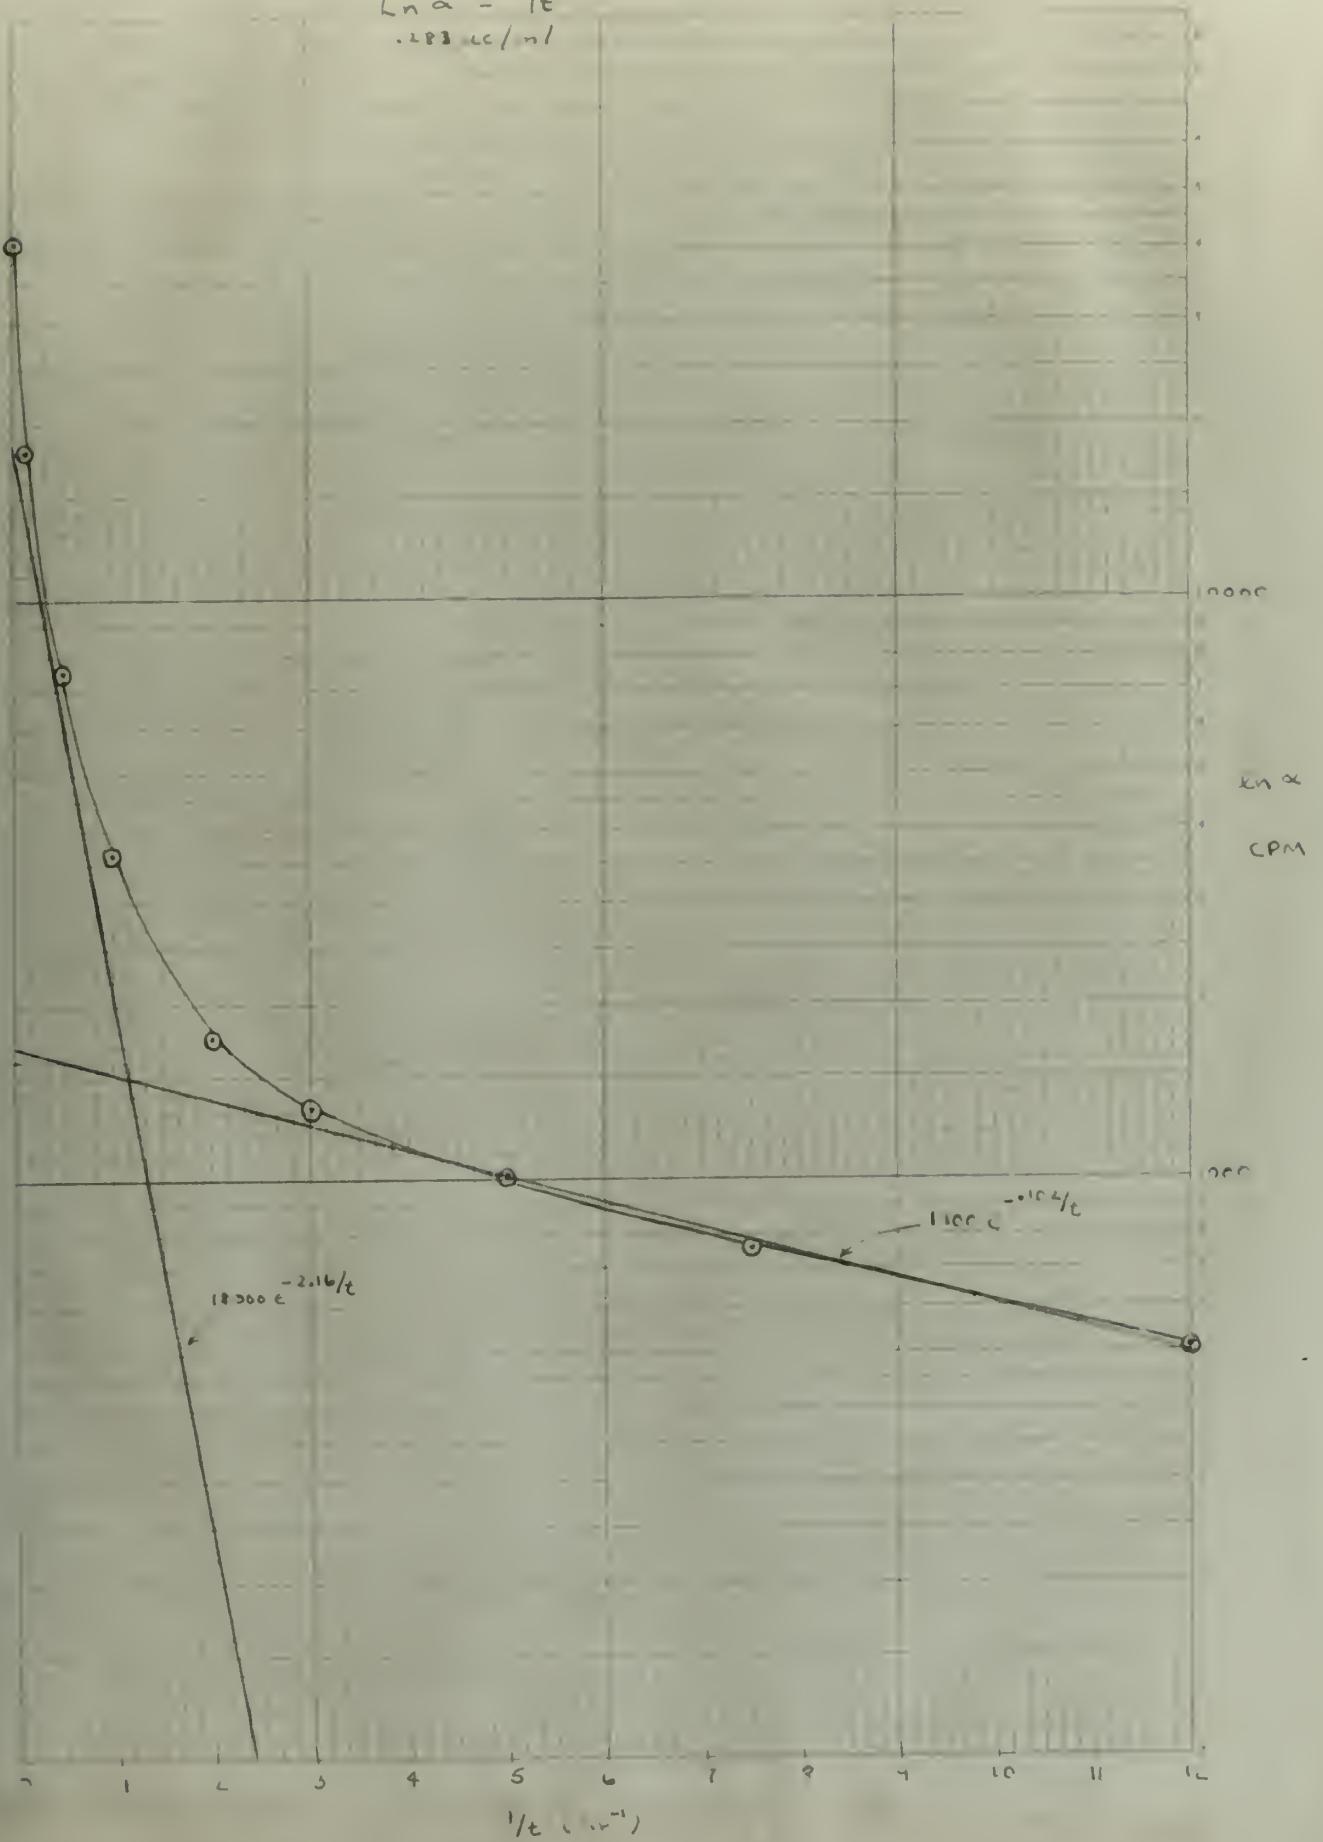




I-2

$\ln \alpha = 1/c$

$.016 \text{ c/hr}$

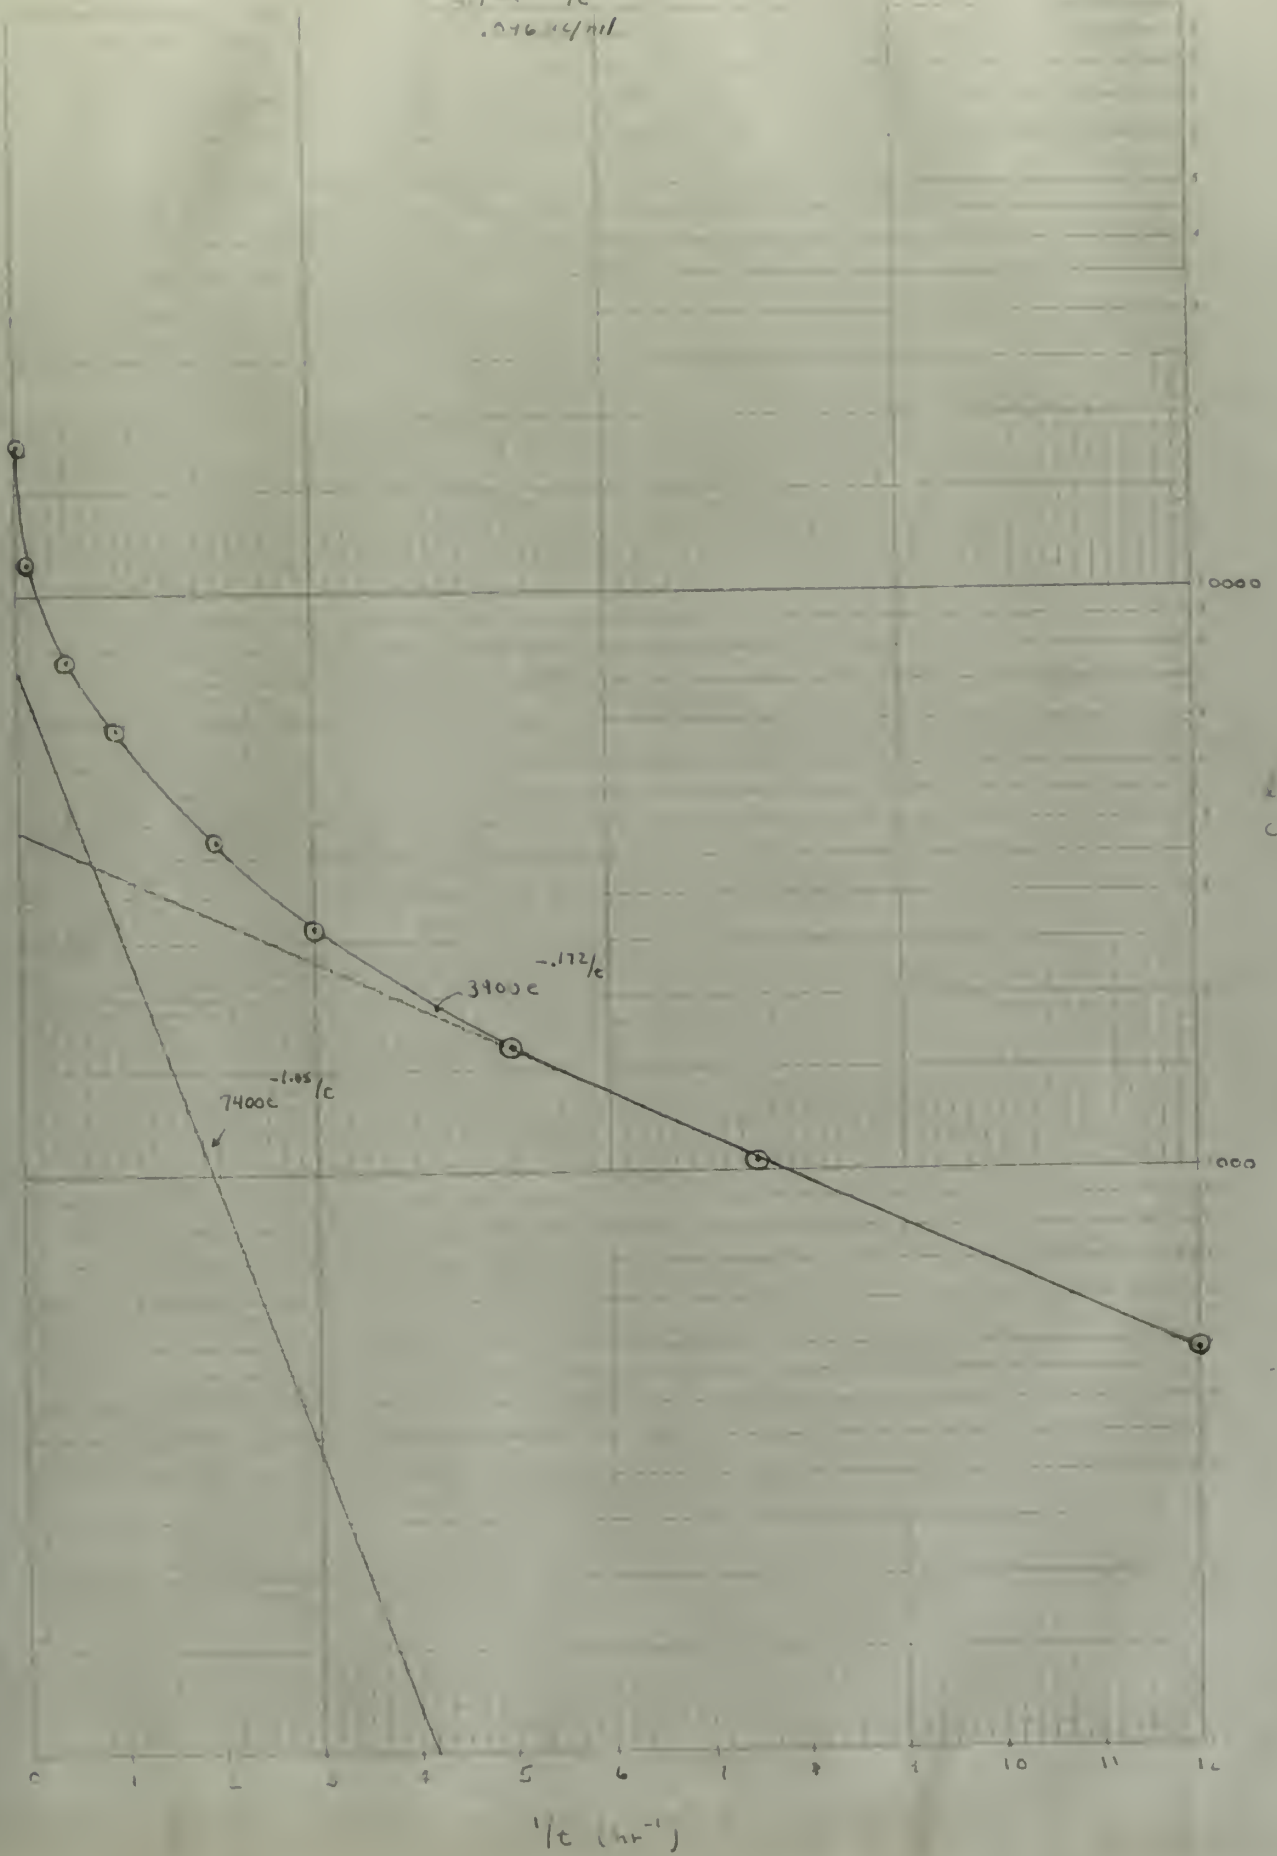



I-3

$\lambda = 1/c$   
 $.0880 \text{ u/mil}$








I-4

$0.000 - 1/e$

$.0005 \pm 1/e$

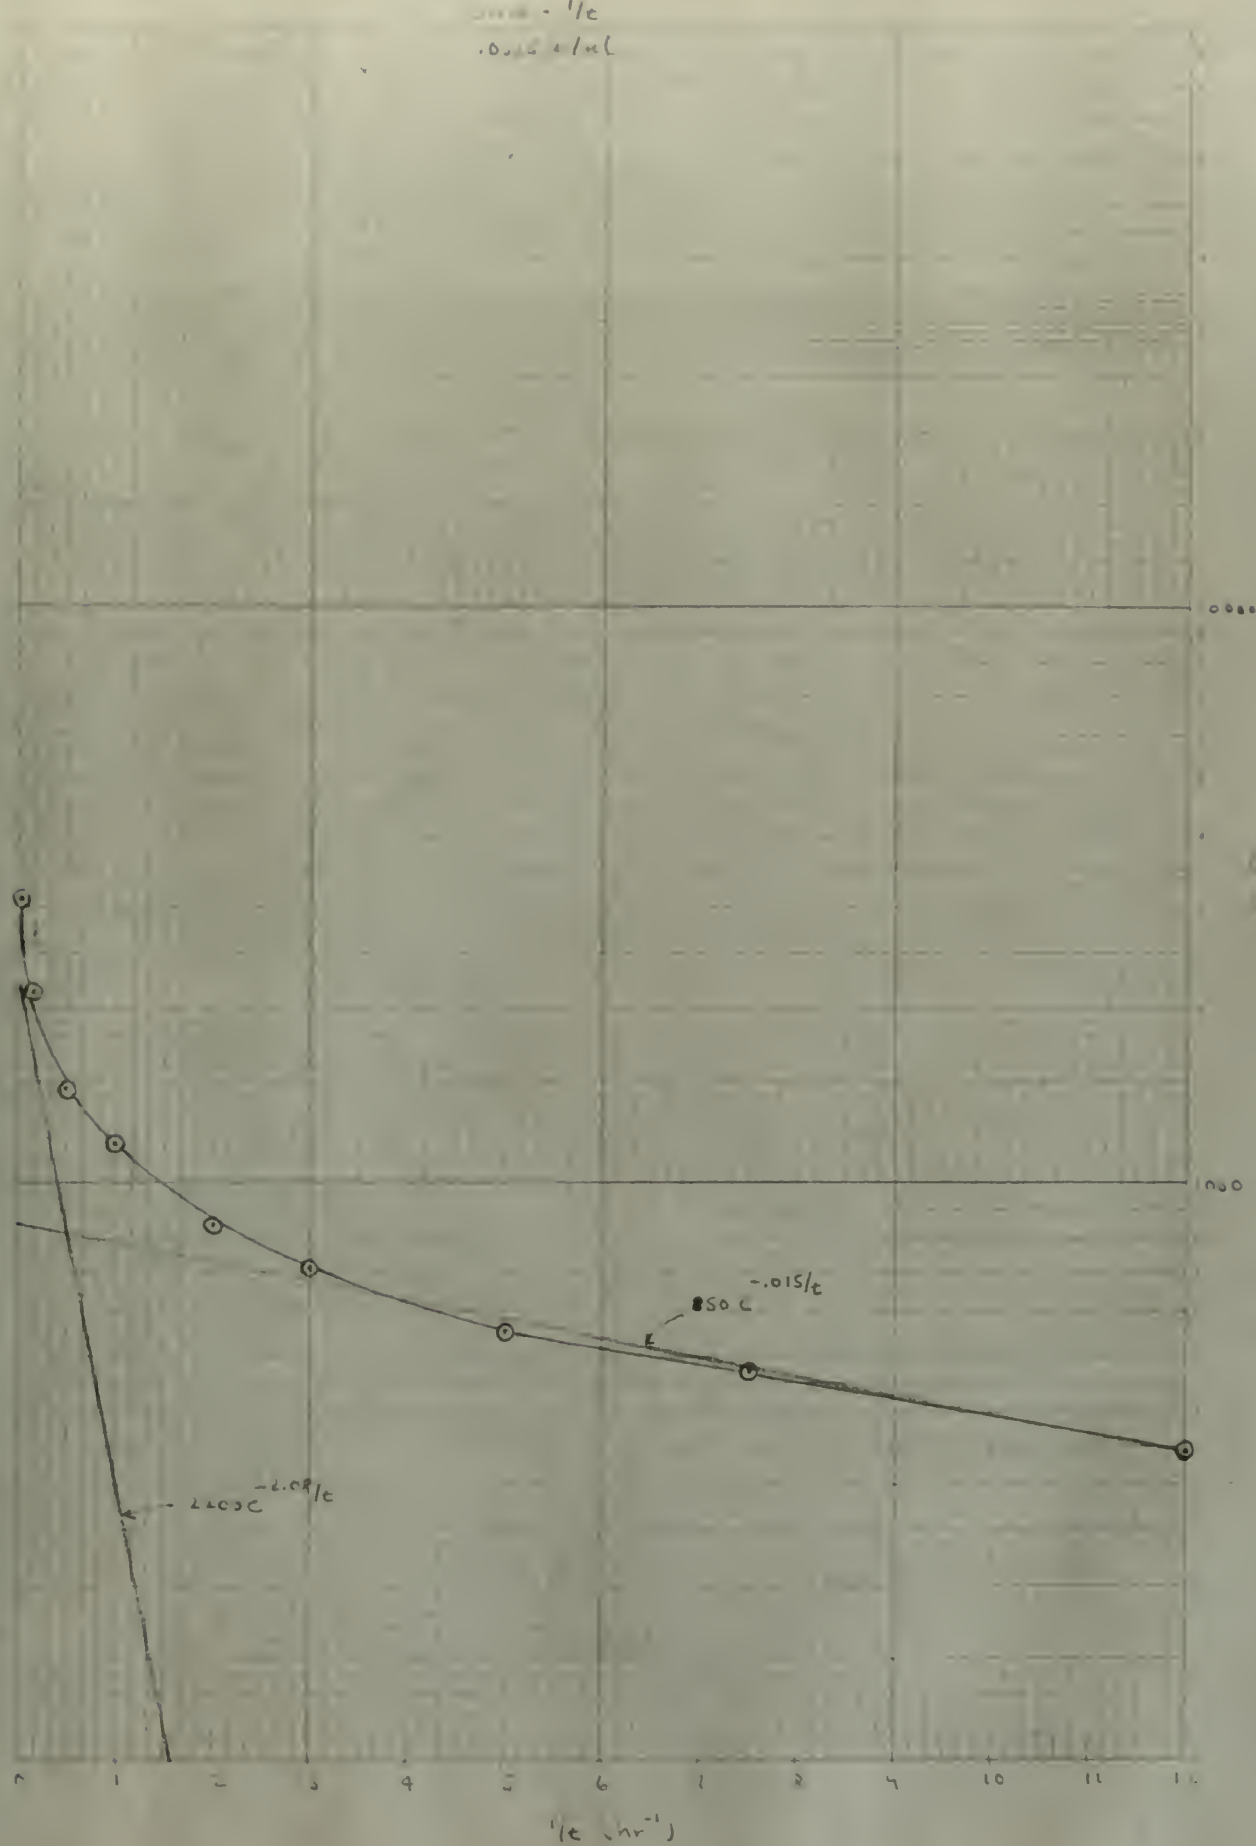



A study of these relations indicates little correspondence between the changes in the various constants and the changes in concentration. This lack of correspondence indicates that concentration effects may easily be obscured by the action of surface imperfections. These results may also indicate that control of concentration was not as precise as expected. This is possible since the amount of substances, other than radioactive iodine, which may have been present in the active material as purchased could easily vary from lot to lot, both as to type and amount of material.

As a possible explanation of the lack of correspondence, we may postulate that the linear portion of the curve, which extends on the average for 12 to 20 minutes, represents a particular adsorption process which is more sensitive to variations in surface than it is to concentration changes. The second portion of the curve is believed to indicate a second process which initially is negligible in extent. This process might be more readily influenced by concentration changes, although it would also be affected by the initial process which had been and was still going on.

The possibilities outlined above receive some support from the curve plotted on graph I-2 as it is compared to the others in the group. In this plot, the initial adsorption occurs at a higher rate than in the other runs, indicating a surface physically more receptive to the adsorptive. This in turn enables a more rapid build-up of the amount of iodide, with the second phase becoming significant sooner than it might otherwise. In this case the second process takes place less rapidly despite its earlier start, probably because the initial process is still important and taking



place at a significant rate. These two processes must compete for the available adsorptive and hence the effect on the second. In the other runs, the second phase does not become significant as soon, but when it does appear, it does so much more rapidly since the initial adsorption process is more nearly complete.


Surface effects are clearly shown by graphs II and III. The first of these shows the plots of two runs which resulted in marked deviations from the adsorption pattern previously noted. In the upper plot, the planchets followed the normal pattern for the first 30 minutes, and thereafter showed little tendency to adsorb any more iodide. In the light of the postulations of a two-phase process, it would appear here that for some reason the second phase did not proceed at its usual rate, and that the initial adsorption process was only slightly augmented by it. The cause here was unknown, and led to an experiment which produced the lower plot. Here the planchets were prepared in the usual manner, and then were left to soak in a water bath for five days prior to immersion in the active solution. This technique led to the results shown, which indicate that here the first process was grossly inhibited, probably because the available sites were occupied by water molecules. Eventually, after the first 20 minutes, the second phase started and began to build up the surface activity. Since it was possible, by means of surface effects, to inhibit the initial process, it is believed that surface effects could also lead to inhibition of the second process, thus offering a possible explanation of the results shown in the upper plot.





II

$\ln x - 1/c$   
 $.1085 \mu\text{c/ml}$

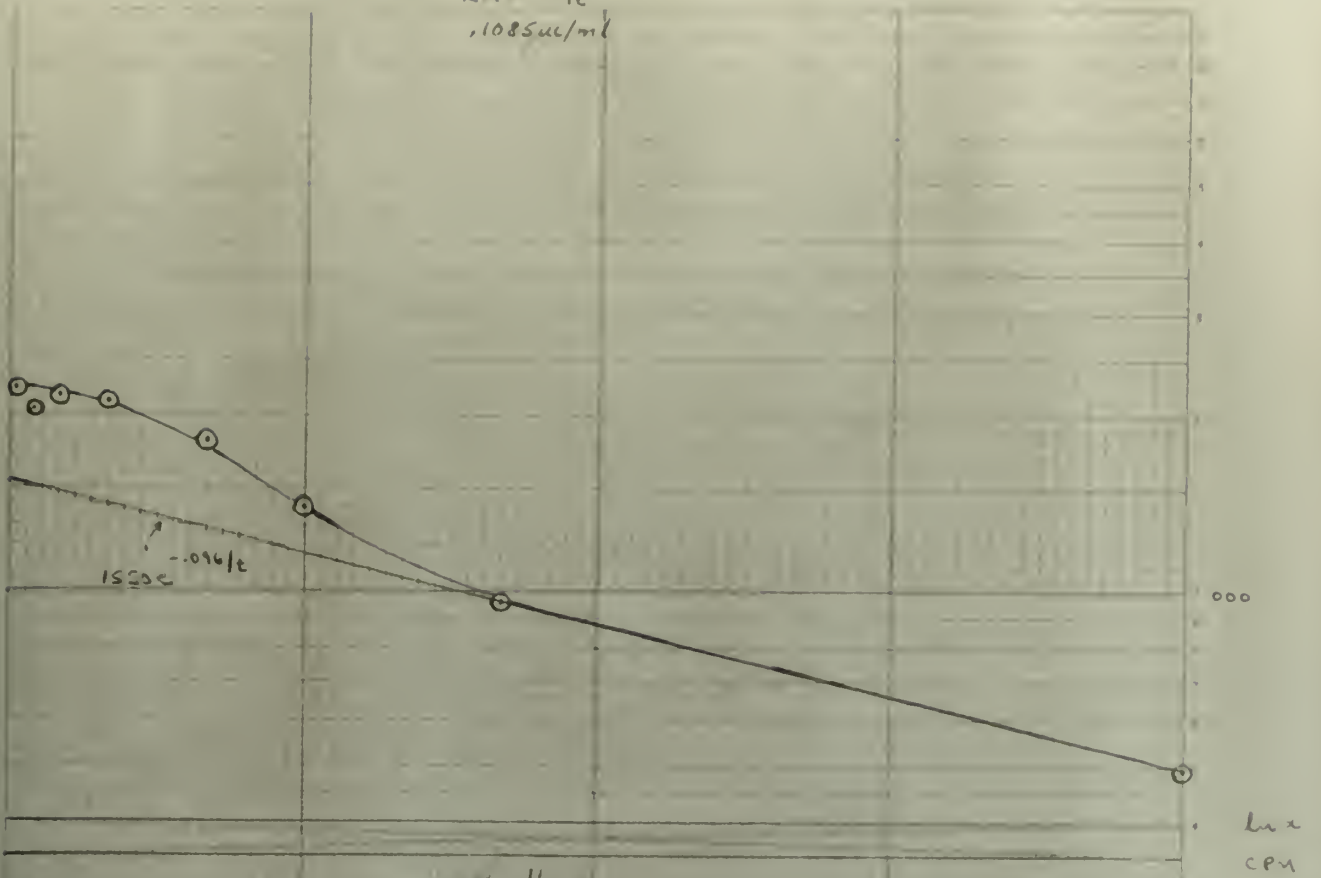

$\ln x - 1/c$   
 $.0905 \mu\text{c/ml}$



$1/c (\text{hr}^{-1})$





# GRAPH III


Illustration of Surface Effect

$\log$  Activity vs Reciprocal Time

(○) Single Planchet

(●) Average of Five Similar Planchets

Concentration .0325  $\mu$ /ml

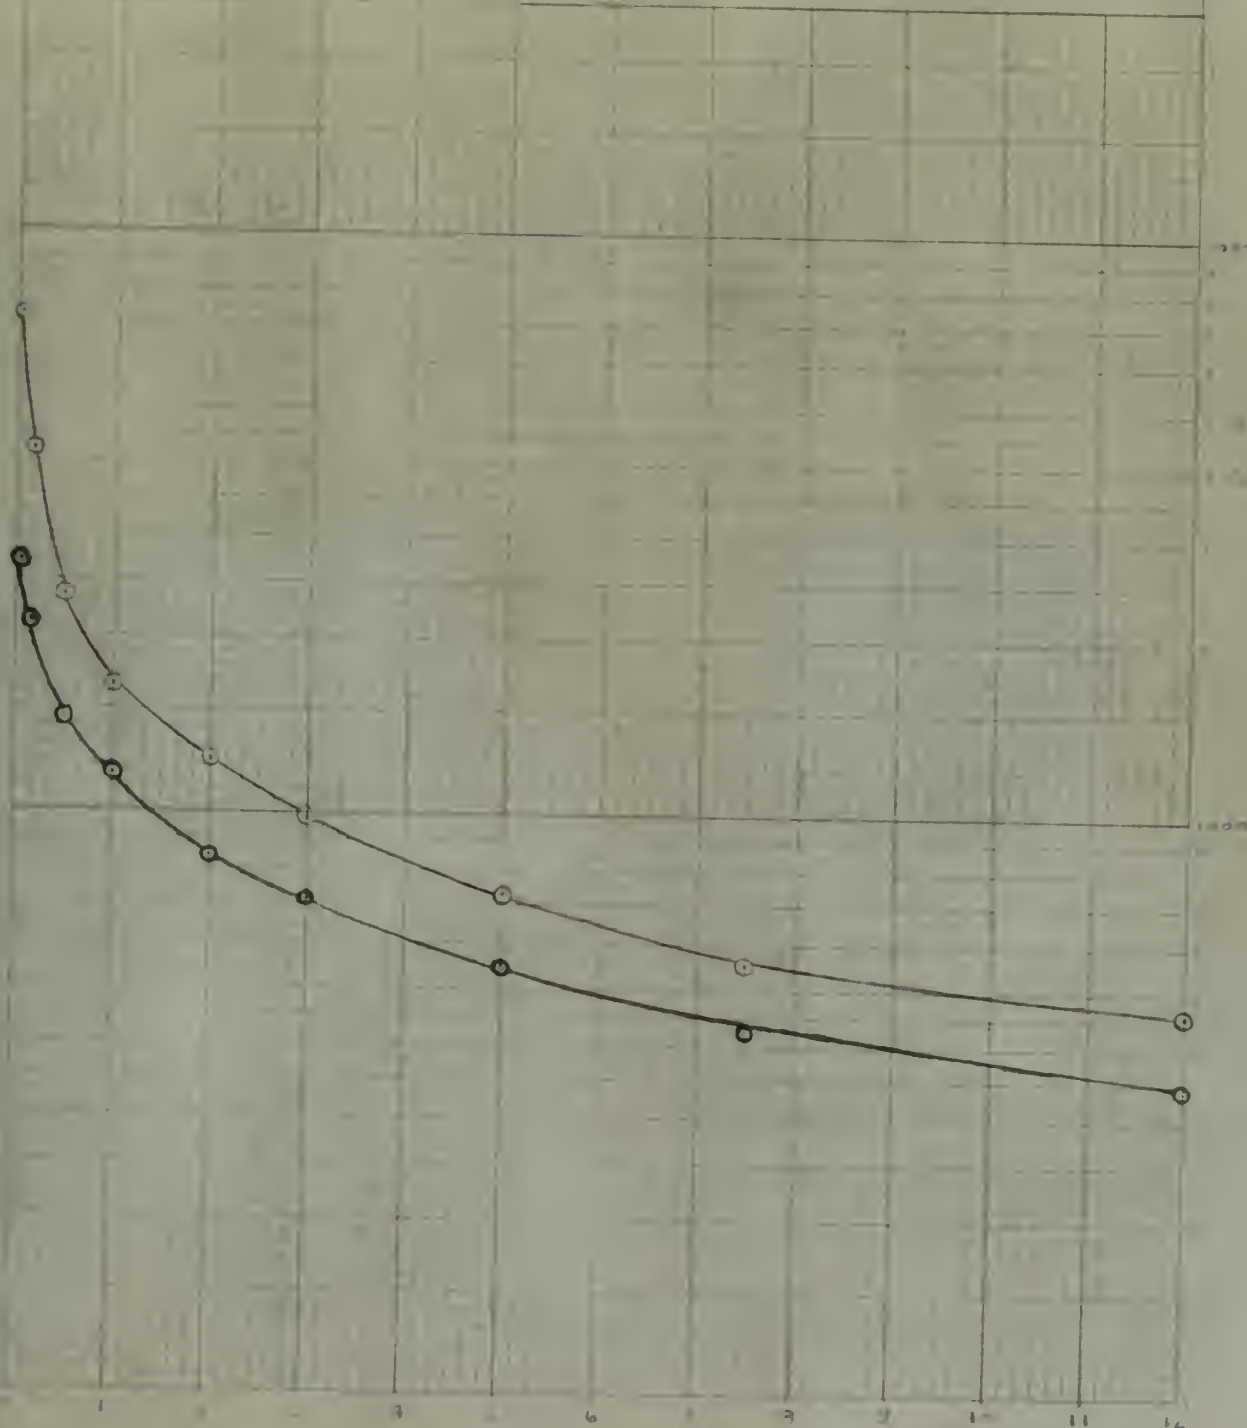

$1/t$  (sec<sup>-1</sup>)



Graph III shows the variation in activity obtained in a particular run using six planchets. One plot represents the average activity on five of the planchets, and the other is a plot of the activity on the remaining planchet. All of the planchets had received identical preparatory treatment and all were immersed in the same solution for the same periods of time. The parallel nature of the curves indicates that surface imperfections may influence the amount of adsorptive that can be collected on the surface without necessarily influencing the general pattern of rate.

A further study of the effects of surface imperfections was made by means of radio-autographs. The planchets from a particular test series were placed on photographic plates and permitted to remain for about 24 hours, after which the plates were developed in the usual manner. The plates were then printed and the results of four of the plates reproduced below.



Planchet #1



Planchet #2



Planchet #3



Planchet #4

The first planchet was the most active of the group, and clearly in evidence are the numerous hot spots or "active centers" spread over the surface. The reproduction is not so clear as the original plate in this particular feature. The other planchets, in decreasing order of activity,





are #3, #4, and #2. On the last planchet, #2, there is a quite uniform appearance to the spread of activity, with almost no noticeable hot spots. Microscopic examination of these same planchets indicated some pitting in the general location of these spots. In general, cracks and fissures were not represented by corresponding concentrations of activity, and this may be due to the bridging of these imperfections by interaction in a lateral sense by the adsorbed molecules.

Graph IV shows the pattern of rate of adsorption. It is clear that the initial rate of adsorption is very high, with an extremely rapid fall-off to low rates within a few hours at most. This follows the pattern which was previously shown in this paper to be among the results of other workers in this field. It also shows a tendency toward equilibrium, in that the rates appear to be falling rapidly toward zero. The low concentration run is most clear in this respect.

Although the empirical relation presented in this paper contains two terms which appear to represent two phases or processes, it may well be that additional terms and hence processes exist. Additional study would be necessary to enlarge upon this possibility. In further studies of this type, it may be advisable to take steps to insure absolute control of concentration in order to isolate this effect from complicating factors. One such step could be to add relatively large amounts of carrier iodine to the solution, using the active iodine in tracer quantities as a measure of adsorption. In this way impurities in the active material would have little effect upon the adsorption process.

The data obtained during this study is of insufficient volume to permit definite conclusions to be made, but certainly there are indic-






GRAPH IV

Rate of Adsorption

Activity (CPM)/HR v Time

- 0.001 M
- △ 0.002 M
- 0.005 M

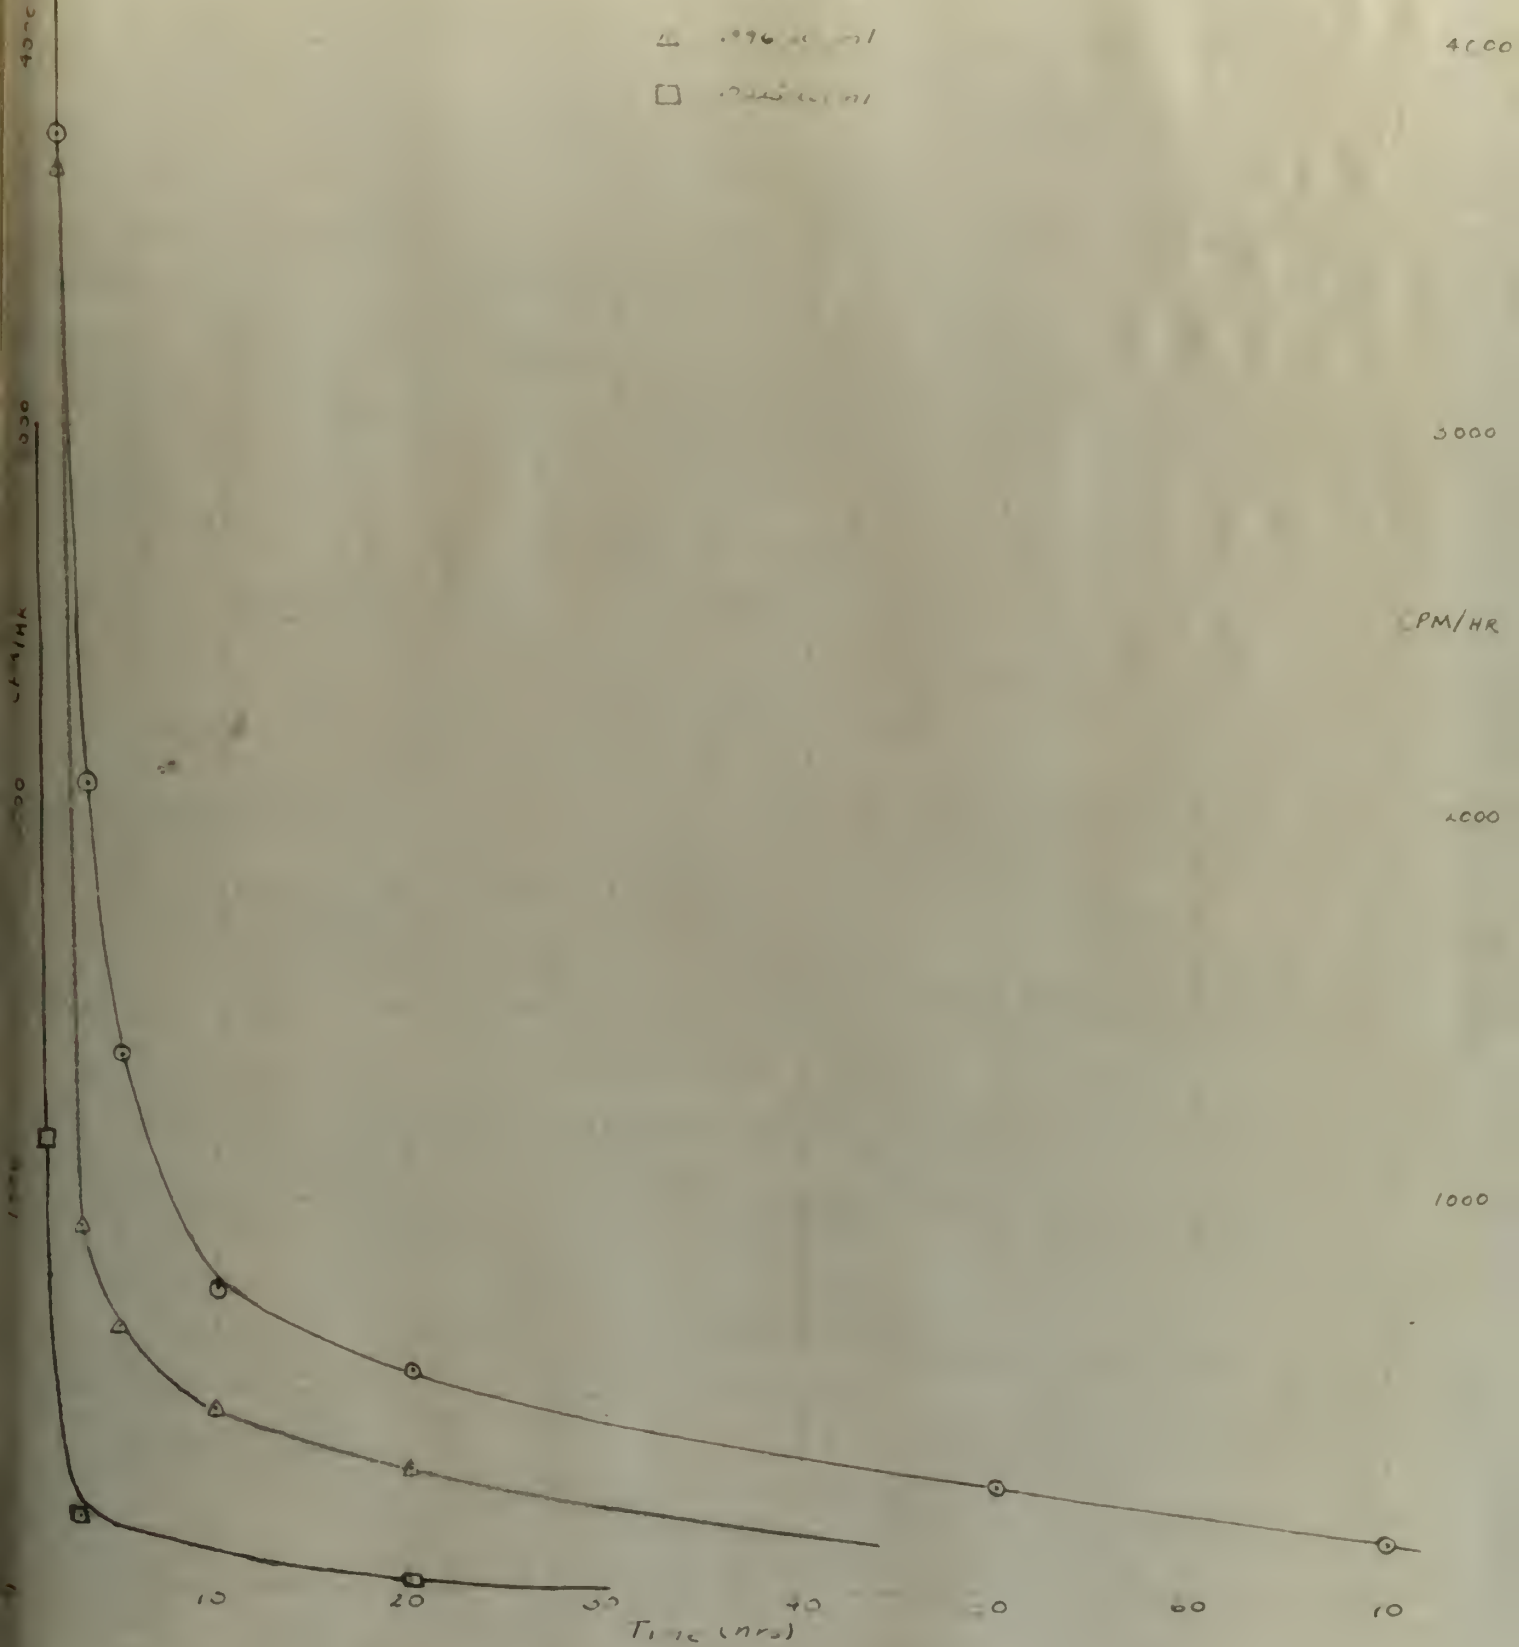



ations that the overall process may consist of two or more phases, each of which may be affected by the many other complicating factors which may be present. Surfaces are extremely important in adsorption. Careful preparation of the adsorbent may help to minimize surface effects, but it is doubtful if they can be eliminated completely. A factor which may be important, even though only faintly suggested by these data, is pH. The use of an acid bath in preparation of the planchets in this study may have changed the pH slightly in the immediate vicinity of the interface. Indeed, this may have been the mechanism in the case of the water-soaked planchets, since in this case it is doubtful that any acid was left on the planchets after their prolonged water bath. In any event, a study of pH effects would be of considerable interest.



## BIBLIOGRAPHY

1. Getman, FH and Daniels, F, Outlines of Physical Chemistry. John Wiley and Sons, New York, 1940
2. Cassidy, HG, Adsorption and Chromatography. Interscience Press, New York, 1951
3. Adam, NK, The Physics and Chemistry of Surfaces, 3rd Ed, Oxford University Press, London, 1941
4. Frazer, Patrick, and Smith, HE, J Phys Chem, 31, 897 (1927)
5. Russell, AS and Stokes, JJ Jr, J Am Chem Soc, 69, 1312 (1947)
6. King and Schochet, J Phys Chem, 57, 895-8 (1953)
7. Rydberg and Rydberg, Svensk Kem Tidskr, 64, 200-11 (1952)



SERIES #1

Determination of Concentration

| Date & Time | Amount of Solution | Counts | Time      | CPM  | CPM less background | Activity        | Activity corrected for Decay |
|-------------|--------------------|--------|-----------|------|---------------------|-----------------|------------------------------|
| 8 Mar 0900  | .106ml             | 8192   | 56.6 sec  | 8590 | 8560                | .283 $\mu$ c/ml | .283 $\mu$ c/ml              |
| 15 Mar 0900 | .105ml             | 8192   | 106.0 sec | 4640 | 4602                | .153 $\mu$ c/ml | .280 $\mu$ c/ml              |

Test Data

| Date & Time | Planchet # | Temp.  | Total Immersion Time | Counts | Time      | CPM  | Background | CPM Corrected for Decay |
|-------------|------------|--------|----------------------|--------|-----------|------|------------|-------------------------|
| 8 Mar 0900  | 1          | 23.3°C | 5 min.               | 8192   | 865.5 sec | 568  | 538        | 538                     |
| "           | 2          | "      | "                    | 4096   | 381.0     | 644  | 614        | 614                     |
| 0930        | 3          | "      | "                    | "      | 472.7     | 520  | 490        | 490                     |
| "           | 4          | "      | "                    | "      | 562.0     | 436  | 406        | 406                     |
| 1000        | 5          | "      | "                    | "      | 427.5     | 574  | 544        | 544                     |
| "           | 6          | "      | "                    | "      | 491.2     | 500  | 470        | 470                     |
| 8 Mar 1230  | 1          | 23.3°C | 8 min.               | 4096   | 281.5     | 874  | 844        | 844                     |
| "           | 2          | "      | "                    | "      | 259.0     | 948  | 918        | 918                     |
| 1245        | 3          | "      | "                    | "      | 367.6     | 668  | 638        | 638                     |
| "           | 4          | "      | "                    | "      | 369.5     | 665  | 635        | 635                     |
| 1300        | 5          | "      | "                    | "      | 288.4     | 864  | 834        | 834                     |
| "           | 6          | "      | "                    | "      | 328.0     | 749  | 719        | 719                     |
| 8 Mar 1310  | 1          | 23.3°C | 12 min.              | 4096   | 235.5     | 1041 | 1011       | 1011                    |
| "           | 2          | "      | "                    | "      | 218.0     | 1128 | 1098       | 1098                    |
| 1320        | 3          | "      | "                    | "      | 255.0     | 962  | 932        | 932                     |
| "           | 4          | "      | "                    | "      | 319.0     | 770  | 740        | 740                     |
| 1335        | 5          | "      | "                    | "      | 183.5     | 1340 | 1310       | 1310                    |
| "           | 6          | "      | "                    | "      | 253.6     | 970  | 940        | 940                     |
| 8 Mar 1345  | 1          | 23.3°C | 20 min.              | 4096   | 186.0     | 1321 | 1291       | 1291                    |
| "           | 2          | "      | "                    | "      | 166.0     | 1480 | 1450       | 1450                    |
| 1355        | 3          | "      | "                    | "      | 201.8     | 1220 | 1190       | 1190                    |
| "           | 4          | "      | "                    | "      | 227.0     | 1081 | 1051       | 1051                    |
| 1410        | 5          | "      | "                    | "      | 156.5     | 1570 | 1540       | 1540                    |
| "           | 6          | "      | "                    | "      | 174.0     | 1411 | 1381       | 1381                    |
| 8 Mar 1435  | 1          | 23.3°C | 30 min.              | 8192   | 301.0     | 1632 | 1602       | 1602                    |
| "           | 2          | "      | "                    | "      | 265.0     | 1854 | 1824       | 1824                    |
| 1445        | 3          | "      | "                    | "      | 314.2     | 1563 | 1533       | 1533                    |
| "           | 4          | "      | "                    | "      | 339.5     | 1449 | 1419       | 1419                    |
| 1455        | 5          | "      | "                    | "      | 230.0     | 2140 | 2110       | 2110                    |
| "           | 6          | "      | "                    | "      | 254.0     | 1936 | 1906       | 1906                    |
| 8 Mar 1510  | 1          | 23.3°C | 1 hr.                | 8192   | 130.2     | 3775 | 3745       | 3745                    |
| "           | 2          | "      | "                    | "      | 159.4     | 3081 | 3051       | 3051                    |
| 1520        | 3          | "      | "                    | "      | 155.8     | 3160 | 3130       | 3130                    |
| "           | 4          | "      | "                    | "      | 133.8     | 3680 | 3650       | 3650                    |
| 1530        | 5          | "      | "                    | "      | 129.5     | 3790 | 3760       | 3760                    |
| "           | 6          | "      | "                    | "      | 108.5     | 4530 | 4500       | 4500                    |





|             |      | Total      |        |                |        |       |       | CPM Corrected for |       |
|-------------|------|------------|--------|----------------|--------|-------|-------|-------------------|-------|
| Date & Time |      | Planchet # | Temp.  | Immersion Time | Counts | Time  | CPM   | Background        | Decay |
| 10 Mar      | 0930 | 1          | 23.0°C | 2 hr.          | 12288  | 101.0 | 7295  | 7257              | 8640  |
| "           | "    | 2          | "      | "              | "      | 107.5 | 6850  | 6812              | 8100  |
| "           | "    | 3          | "      | "              | "      | 131.0 | 5620  | 5582              | 6640  |
| "           | "    | 4          | "      | "              | "      | 161.8 | 4555  | 4517              | 5370  |
| "           | "    | 5          | "      | "              | "      | 109.0 | 6760  | 6722              | 8000  |
| "           | "    | 6          | "      | "              | "      | 110.0 | 6690  | 6652              | 7920  |
| 12 Mar      | 1430 | 1          | 23.0°C | 8 hr.          | 12288  | 55.2  | 13310 | 13268             | 19110 |
| "           | "    | 2          | "      | "              | "      | 57.1  | 12890 | 12848             | 18520 |
| "           | "    | 3          | "      | "              | "      | 65.0  | 11320 | 11278             | 16250 |
| "           | "    | 4          | "      | "              | "      | 80.0  | 9210  | 9168              | 13240 |
| "           | "    | 5          | "      | "              | "      | 60.0  | 12288 | 12246             | 17690 |
| "           | "    | 6          | "      | "              | "      | 59.5  | 12390 | 12348             | 17810 |
| 15 Mar      | 1000 | 1          | 23.0°C | 75 hr.         | 16384  | 37.0  | 26550 | 26512             | 48700 |
| "           | "    | 2          | "      | "              | "      | 41.0  | 23990 | 23952             | 44000 |
| "           | "    | 3          | "      | "              | "      | 41.5  | 23650 | 23612             | 43500 |
| "           | "    | 4          | "      | "              | "      | 67.5  | 14550 | 14512             | 26750 |
| "           | "    | 5          | "      | "              | "      | 44.0  | 22350 | 22312             | 41000 |
| "           | "    | 6          | "      | "              | "      | 42.0  | 23400 | 23362             | 42900 |



# SERIES #2

## Determination of Concentration

| Date & Time | Amount of Solution | Counts | Time     | CPM  | CPM less background | Activity         | Activity corrected for Decay |
|-------------|--------------------|--------|----------|------|---------------------|------------------|------------------------------|
| 29 Mar 1530 | .100ml             | 2048   | 44.0 sec | 2795 | 2755                | .0960 $\mu$ c/ml | .0960 $\mu$ c/ml             |
| 1 Apr 1000  | .100ml             | 2048   | 56.5 sec | 2180 | 2140                | .0747 $\mu$ c/ml | .0952 $\mu$ c/ml             |

## Test Data

| Date & Time | Planchet # | Temp.             | Total Immersion Time | Counts | Time      | CPM   | CPM Corrected for Background | Decay |
|-------------|------------|-------------------|----------------------|--------|-----------|-------|------------------------------|-------|
| 29 Mar 1530 | 1          | 23.3 $^{\circ}$ c | 5min.                | 4096   | 124.0 sec | 1980  | 1940                         | 1940  |
| "           | 2          | "                 | "                    | "      | 426.0     | 577   | 537                          | 537   |
| "           | 3          | "                 | "                    | 2048   | 253.0     | 486   | 446                          | 446   |
| "           | 4          | "                 | "                    | "      | 231.0     | 532   | 492                          | 492   |
| "           | 5          | "                 | "                    | "      | 208.0     | 591   | 551                          | 551   |
| "           | 6          | "                 | "                    | "      | 245.0     | 502   | 462                          | 462   |
| 30 Mar 0900 | 1          | 20.0 $^{\circ}$ c | 8 min.               | 2048   | 36.0      | 3420  | 3280                         | 3490  |
| "           | 2          | "                 | "                    | "      | 108.7     | 1132  | 992                          | 1055  |
| "           | 3          | "                 | "                    | "      | 107.0     | 1150  | 1010                         | 1074  |
| "           | 4          | "                 | "                    | "      | 121.5     | 1012  | 872                          | 929   |
| "           | 5          | "                 | "                    | "      | 108.0     | 1140  | 1000                         | 1065  |
| "           | 6          | "                 | "                    | "      | 106.0     | 1160  | 1020                         | 1085  |
| 30 Mar 0930 | 1          | 20.0 $^{\circ}$ c | 12 min.              | 2048   | 23.2      | 5300  | 5160                         | 5500  |
| "           | 2          | "                 | "                    | "      | 79.0      | 1558  | 1418                         | 1510  |
| 0940        | 3          | "                 | "                    | "      | 89.5      | 1372  | 1338                         | 1422  |
| "           | 4          | "                 | "                    | "      | 91.2      | 1350  | 1316                         | 1400  |
| "           | 5          | "                 | "                    | "      | 75.8      | 1621  | 1587                         | 1690  |
| "           | 6          | "                 | "                    | "      | 62.5      | 1970  | 1936                         | 2060  |
| 30 Mar 1000 | 1          | 21.0 $^{\circ}$ c | 20 min.              | 4096   | 34.0      | 7230  | 7196                         | 7700  |
| "           | 2          | "                 | "                    | "      | 117.0     | 2100  | 2066                         | 2215  |
| "           | 3          | "                 | "                    | "      | 118.0     | 2080  | 2046                         | 2190  |
| "           | 4          | "                 | "                    | "      | 103.2     | 2380  | 2346                         | 2515  |
| "           | 5          | "                 | "                    | "      | 89.4      | 2750  | 2716                         | 2905  |
| "           | 6          | "                 | "                    | "      | 75.5      | 3255  | 3221                         | 3450  |
| 30 Mar 1100 | 1          | 21.0 $^{\circ}$ c | 30 min.              | 4096   | 27.0      | 9100  | 9066                         | 9710  |
| "           | 2          | "                 | "                    | "      | 84.5      | 2910  | 2876                         | 3080  |
| "           | 3          | "                 | "                    | "      | 84.0      | 2930  | 2896                         | 3100  |
| "           | 4          | "                 | "                    | "      | 70.0      | 3510  | 3476                         | 3720  |
| "           | 5          | "                 | "                    | "      | 60.5      | 4060  | 4026                         | 4310  |
| "           | 6          | "                 | "                    | "      | 57.2      | 4290  | 4256                         | 4560  |
| 30 Mar 1130 | 1          | 21.0 $^{\circ}$ c | 1 hr.                | 8192   | 41.0      | 12000 | 11966                        | 12880 |
| "           | 2          | "                 | "                    | "      | 110.0     | 4460  | 4426                         | 4760  |
| "           | 3          | "                 | "                    | "      | 105.0     | 4680  | 4646                         | 4998  |
| "           | 4          | "                 | "                    | "      | 92.0      | 5340  | 5306                         | 5700  |
| "           | 5          | "                 | "                    | "      | 76.3      | 6440  | 6406                         | 6890  |
| "           | 6          | "                 | "                    | "      | 70.2      | 7000  | 6966                         | 7495  |



| Date & Time | Planchet # | Temp.  | Total Immersion |  | Counts | Time | CPM   | CPM Corrected for |       |
|-------------|------------|--------|-----------------|--|--------|------|-------|-------------------|-------|
|             |            |        | Time            |  |        |      |       | Background        | Decay |
| 30 Mar 1400 | 1          | 22.0°C | 2 hr.           |  | 8192   | 38.8 | 12690 | 12656             | 13710 |
| "           | 2          | "      | "               |  | "      | 82.8 | 5940  | 5906              | 6400  |
| "           | 3          | "      | "               |  | "      | 77.8 | 6320  | 6286              | 6810  |
| "           | 4          | "      | "               |  | "      | 71.0 | 6920  | 6886              | 7460  |
| "           | 5          | "      | "               |  | "      | 61.8 | 7950  | 7916              | 8580  |
| "           | 6          | "      | "               |  | "      | 57.0 | 8610  | 8576              | 9300  |
| 31 Mar 1430 | 1          | 22.0°C | 7.75 hrs.       |  | 8192   | 32.7 | 15010 | 14961             | 17700 |
| "           | 2          | "      | "               |  | "      | 54.2 | 9060  | 9011              | 10690 |
| "           | 3          | "      | "               |  | "      | 51.0 | 9640  | 9591              | 11380 |
| "           | 4          | "      | "               |  | "      | 52.0 | 9450  | 9401              | 11120 |
| "           | 5          | "      | "               |  | "      | 46.4 | 10600 | 10551             | 12500 |
| "           | 6          | "      | "               |  | "      | 48.7 | 10100 | 10051             | 11900 |
| 1 Apr 0950  | 1          | 21.0°C | 27.0 hr         |  | 8192   | 24.9 | 19720 | 19670             | 24900 |
| "           | 2          | "      | "               |  | "      | 38.0 | 12920 | 12870             | 16290 |
| "           | 3          | "      | "               |  | "      | 34.2 | 14390 | 14340             | 18190 |
| "           | 4          | "      | "               |  | "      | 36.0 | 13650 | 13600             | 17220 |
| "           | 5          | "      | "               |  | "      | 31.0 | 15870 | 15810             | 20050 |
| "           | 6          | "      | "               |  | "      | 35.0 | 14050 | 14000             | 17730 |





# SERIES #3

## Determination of Concentration

| Date & Time | Amount of Solution | Counts | Time      | CPM |                 | Activity         |                     |
|-------------|--------------------|--------|-----------|-----|-----------------|------------------|---------------------|
|             |                    |        |           | CPM | less Background | corrected        | corrected for Decay |
| 5 Apr 1130  | .100ml             | 4096   | 251.7 sec | 977 | 937             | .0328 $\mu$ c/ml | .0328 $\mu$ c/ml    |
| 7 Apr 1300  | .100ml             | 4096   | 297.0 sec | 826 | 775             | .0271 $\mu$ c/ml | .0323 $\mu$ c/ml    |

## Test Data

| Date & Time | Planchet # | Temp.             | Total Immersion |   | Counts | Time      | CPM  | CPM Corrected for |       |
|-------------|------------|-------------------|-----------------|---|--------|-----------|------|-------------------|-------|
|             |            |                   | Time            |   |        |           |      | Background        | Decay |
| 5 Apr 1215  | 1          | 23.9 $^{\circ}$ c | 5 min.          |   | 2048   | 303.0 sec | 406  | 366               | 366   |
| "           | 2          | "                 | "               | " | "      | 341.2     | 361  | 321               | 321   |
| "           | 3          | "                 | "               | " | "      | 329.2     | 374  | 334               | 334   |
| "           | 4          | "                 | "               | " | "      | 351.5     | 350  | 310               | 310   |
| "           | 5          | "                 | "               | " | "      | 246.0     | 500  | 460               | 460   |
| "           | 6          | "                 | "               | " | "      | 291.4     | 422  | 382               | 382   |
| 5 Apr 1250  | 1          | 23.9 $^{\circ}$ c | 8 min.          |   | 2048   | 254.0     | 484  | 444               | 444   |
| "           | 2          | "                 | "               | " | "      | 289.0     | 426  | 386               | 386   |
| "           | 3          | "                 | "               | " | "      | 266.2     | 461  | 421               | 421   |
| "           | 4          | "                 | "               | " | "      | 294.0     | 418  | 378               | 378   |
| "           | 5          | "                 | "               | " | "      | 206.0     | 596  | 556               | 556   |
| "           | 6          | "                 | "               | " | "      | 233.2     | 527  | 487               | 487   |
| 5 Apr 1330  | 1          | 23.9 $^{\circ}$ c | 12 min.         |   | 2048   | 204.2     | 601  | 561               | 561   |
| "           | 2          | "                 | "               | " | "      | 229.0     | 537  | 497               | 497   |
| "           | 3          | "                 | "               | " | "      | 231.0     | 532  | 492               | 492   |
| "           | 4          | "                 | "               | " | "      | 244.4     | 502  | 462               | 462   |
| "           | 5          | "                 | "               | " | "      | 158.5     | 776  | 736               | 736   |
| "           | 6          | "                 | "               | " | "      | 184.0     | 669  | 629               | 629   |
| 5 Apr 1400  | 1          | 24.0 $^{\circ}$ c | 20 min.         |   | 2048   | 155.8     | 790  | 750               | 750   |
| "           | 2          | "                 | "               | " | "      | 174.8     | 705  | 665               | 665   |
| "           | 3          | "                 | "               | " | "      | 181.3     | 678  | 638               | 638   |
| "           | 4          | "                 | "               | " | "      | 183.7     | 670  | 630               | 630   |
| "           | 5          | "                 | "               | " | "      | 120.6     | 1021 | 981               | 981   |
| "           | 6          | "                 | "               | " | "      | 139.7     | 881  | 841               | 841   |
| 5 Apr 1430  | 1          | 24.0 $^{\circ}$ c | 30 min.         |   | 2048   | 134.8     | 915  | 875               | 875   |
| "           | 2          | "                 | "               | " | "      | 144.0     | 855  | 815               | 815   |
| "           | 3          | "                 | "               | " | "      | 143.8     | 856  | 816               | 816   |
| "           | 4          | "                 | "               | " | "      | 159.3     | 771  | 731               | 731   |
| "           | 5          | "                 | "               | " | "      | 97.2      | 1268 | 1228              | 1228  |
| "           | 6          | "                 | "               | " | "      | 122.0     | 1009 | 969               | 969   |
| 6 Apr 0915  | 1          | 23.2 $^{\circ}$ c | 1 hr.           |   | 2048   | 95.0      | 1296 | 1251              | 1350  |
| "           | 2          | "                 | "               | " | "      | 121.8     | 1011 | 966               | 1041  |
| "           | 3          | "                 | "               | " | "      | 123.3     | 996  | 951               | 1028  |
| "           | 4          | "                 | "               | " | "      | 128.4     | 958  | 913               | 985   |
| "           | 5          | "                 | "               | " | "      | 78.3      | 1571 | 1526              | 1642  |
| "           | 6          | "                 | "               | " | "      | 94.2      | 1308 | 1263              | 1361  |



| Date & Time | Planchet # | Temp.  | Total     |        | Time  | CPM  | CPM Corrected for |       |
|-------------|------------|--------|-----------|--------|-------|------|-------------------|-------|
|             |            |        | Immersion | Counts |       |      | Background        | Decay |
| 6 Apr 1015  | 1          | 23.2°C | 2 hr.     | 4096   | 152.7 | 1610 | 1565              | 1697  |
| "           | 2          | "      | "         | "      | 194.0 | 1267 | 1222              | 1325  |
| "           | 3          | "      | "         | "      | 198.8 | 1237 | 1192              | 1292  |
| "           | 4          | "      | "         | "      | 216.0 | 1138 | 1093              | 1187  |
| "           | 5          | "      | "         | "      | 111.0 | 2215 | 2170              | 2355  |
| "           | 6          | "      | "         | "      | 139.5 | 1760 | 1715              | 1860  |
| 6 Apr 1430  | 1          | 24.0°C | 6 hr.     | 4096   | 105.4 | 2325 | 2280              | 2495  |
| "           | 2          | "      | "         | "      | 140.0 | 1755 | 1710              | 1870  |
| "           | 3          | "      | "         | "      | 142.5 | 1723 | 1678              | 1835  |
| "           | 4          | "      | "         | "      | 163.5 | 1502 | 1457              | 1591  |
| "           | 5          | "      | "         | "      | 62.8  | 3915 | 3870              | 4240  |
| "           | 6          | "      | "         | "      | 91.0  | 2700 | 2655              | 2905  |
| 7 Apr 1145  | 1          | 24.0°C | 27 hr.    | 4096   | 82.0  | 3000 | 2949              | 3475  |
| "           | 2          | "      | "         | "      | 97.8  | 2515 | 2464              | 2905  |
| "           | 3          | "      | "         | "      | 110.8 | 2220 | 2169              | 2555  |
| "           | 4          | "      | "         | "      | 119.2 | 2060 | 2009              | 2365  |
| "           | 5          | "      | "         | "      | 39.5  | 6210 | 6169              | 7260  |
| "           | 6          | "      | "         | "      | 67.0  | 3665 | 3614              | 4260  |



SERIES #4

Determination of Concentration

| Date & Time | Amount<br>of<br>Solution | Counts | Time     | CPM  |                    | Activity               |
|-------------|--------------------------|--------|----------|------|--------------------|------------------------|
|             |                          |        |          | CPM  | less<br>Background |                        |
| 12 Apr 1000 | .108ml                   | 4096   | 72.5 sec | 3390 | 3353               | .1085 $\mu\text{c/ml}$ |

Test Data

| Date & Time | Planchet # | Temp.  | Total<br>Immersion |        | CPM Corrected for |      |            |       |
|-------------|------------|--------|--------------------|--------|-------------------|------|------------|-------|
|             |            |        | Time               | Counts | Time              | CPM  | Background | Decay |
| 12 Apr 1030 | 1          | 24.0°C | 5 min.             | 2048   | 249.0 sec         | 494  | 447        | 447   |
| "           | 2          | "      | "                  | "      | 321.3             | 395  | 358        | 358   |
| "           | 3          | "      | "                  | "      | 256.0             | 481  | 444        | 444   |
| "           | 4          | "      | "                  | "      | 218.0             | 564  | 527        | 527   |
| "           | 5          | "      | "                  | "      | 189.7             | 649  | 612        | 612   |
| "           | 6          | "      | "                  | "      | 211.2             | 583  | 546        | 546   |
| 12 Apr 1100 | 1          | 24.0°C | 12 min.            | 4096   | 289.0             | 850  | 813        | 813   |
| "           | 2          | "      | "                  | "      | 330.0             | 744  | 707        | 707   |
| "           | 3          | "      | "                  | "      | 266.0             | 924  | 887        | 887   |
| "           | 4          | "      | "                  | "      | 222.5             | 1102 | 1065       | 1065  |
| "           | 5          | "      | "                  | "      | 200.8             | 1221 | 1184       | 1184  |
| "           | 6          | "      | "                  | "      | 217.2             | 1130 | 1093       | 1093  |
| 12 Apr 1130 | 1          | 24.0°C | 20 min.            | 4096   | 227.0             | 1082 | 1045       | 1045  |
| "           | 2          | "      | "                  | "      | 236.0             | 999  | 962        | 962   |
| "           | 3          | "      | "                  | "      | 176.8             | 1390 | 1333       | 1333  |
| "           | 4          | "      | "                  | "      | 155.7             | 1580 | 1543       | 1543  |
| "           | 5          | "      | "                  | "      | 125.0             | 1968 | 1931       | 1931  |
| "           | 6          | "      | "                  | "      | 154.8             | 1589 | 1552       | 1552  |
| 12 Apr 1200 | 1          | 24.0°C | 30 min.            | 4096   | 173.3             | 1418 | 1381       | 1381  |
| "           | 2          | "      | "                  | "      | 165.5             | 1485 | 1448       | 1448  |
| "           | 3          | "      | "                  | "      | 129.0             | 1905 | 1868       | 1868  |
| "           | 4          | "      | "                  | "      | 117.0             | 2100 | 2063       | 2063  |
| "           | 5          | "      | "                  | "      | 107.2             | 2285 | 2248       | 2248  |
| "           | 6          | "      | "                  | "      | 132.0             | 1861 | 1824       | 1824  |
| 12 Apr 1230 | 1          | 24.0°C | 1 hr.              | 4096   | 139.3             | 1762 | 1725       | 1725  |
| "           | 2          | "      | "                  | "      | 119.2             | 2060 | 2023       | 2023  |
| "           | 3          | "      | "                  | "      | 121.2             | 2025 | 1988       | 1988  |
| "           | 4          | "      | "                  | "      | 101.0             | 2435 | 2398       | 2398  |
| "           | 5          | "      | "                  | "      | 98.0              | 2510 | 2473       | 2473  |
| "           | 6          | "      | "                  | "      | 117.8             | 2085 | 2048       | 2048  |
| 12 Apr 1345 | 1          | 24.0°C | 2 hr.              | 4096   | 124.8             | 1970 | 1933       | 1933  |
| "           | 2          | "      | "                  | "      | 105.0             | 2340 | 2303       | 2303  |
| "           | 3          | "      | "                  | "      | 126.3             | 1942 | 1905       | 1905  |
| "           | 4          | "      | "                  | "      | 98.2              | 2500 | 2463       | 2463  |
| "           | 5          | "      | "                  | "      | 98.5              | 2495 | 2458       | 2458  |
| "           | 6          | "      | "                  | "      | 126.0             | 1950 | 1913       | 1913  |





| Date & Time | Planchet # | Temp.  | Total<br>Immersion |        | CPM   | CPM Corrected for |       |
|-------------|------------|--------|--------------------|--------|-------|-------------------|-------|
|             |            |        | Time               | Counts |       | Background        | Decay |
| 12 Apr 1545 | 1          | 24.5°C | 4 hr.              | 4096   | 121.2 | 2025              | 1988  |
| "           | 2          | "      | "                  | "      | 107.5 | 2285              | 2248  |
| "           | 3          | "      | "                  | "      | 141.0 | 1742              | 1705  |
| "           | 4          | "      | "                  | "      | 105.0 | 2340              | 2303  |
| "           | 5          | "      | "                  | "      | 109.0 | 2255              | 2218  |
| "           | 6          | "      | "                  | "      | 137.2 | 1790              | 1753  |
| 13 Apr 0730 | 1          | 23.0°C | 19.5 hr            | 4096   | 105.2 | 2325              | 2279  |
| "           | 2          | "      | "                  | "      | 101.7 | 2420              | 2374  |
| "           | 3          | "      | "                  | "      | 132.3 | 1855              | 1809  |
| "           | 4          | "      | "                  | "      | 108.7 | 2260              | 2214  |
| "           | 5          | "      | "                  | "      | 115.8 | 2120              | 2074  |
| "           | 6          | "      | "                  | "      | 145.0 | 1692              | 1646  |





SERIES #5

Determination of Concentration

| Date & Time | Amount of Solution | Counts | Time     | CPM  |                 | Activity         |                    |
|-------------|--------------------|--------|----------|------|-----------------|------------------|--------------------|
|             |                    |        |          | CPM  | less Background | Corrected        | Activity for Decay |
| 13 Apr 0800 | .108ml             | 4096   | 86.2 sec | 2845 | 2799            | .0905 $\mu$ c/ml | .0905 $\mu$ c/ml   |
| 13 Apr 1600 | .108ml             | 4096   | 89.0 sec | 2760 | 2714            | .0879 $\mu$ c/ml | .0905 $\mu$ c/ml   |

Test Data

| Date & Time | Planchet # | Temp.             | Total Immersion |        | CPM Corrected for |     |            |       |
|-------------|------------|-------------------|-----------------|--------|-------------------|-----|------------|-------|
|             |            |                   | Time            | Counts | Time              | CPM | Background | Decay |
| 13 Apr 0800 | 1          | 22.0 $^{\circ}$ c | 5 min.          | 2048   | 343.3 sec         | 358 | 312        | 312   |
| "           | 2          | "                 | "               | 1024   | 706.0             | 87  | 41         | 41    |
| "           | 3          | "                 | "               | "      | 173.7             | 354 | 308        | 308   |
| "           | 4          | "                 | "               | "      | 354.6             | 173 | 127        | 127   |
| "           | 5          | "                 | "               | "      | 470.0             | 131 | 85         | 85    |
| "           | 6          | "                 | "               | "      | 574.0             | 107 | 61         | 61    |
| 13 Apr 0815 | 1          | 22.0 $^{\circ}$ c | 10 min.         | 1024   | 184.7             | 332 | 286        | 286   |
| "           | 2          | "                 | "               | "      | 434.0             | 142 | 96         | 96    |
| "           | 3          | "                 | "               | "      | 234.2             | 262 | 216        | 216   |
| "           | 4          | "                 | "               | "      | 262.4             | 234 | 188        | 188   |
| "           | 5          | "                 | "               | "      | 302.0             | 204 | 158        | 158   |
| "           | 6          | "                 | "               | "      | 528.0             | 116 | 70         | 70    |
| 13 Apr 0930 | 1          | 22.0 $^{\circ}$ c | 20 min.         | 1024   | 452.4             | 136 | 90         | 90    |
| "           | 2          | "                 | "               | "      | 496.0             | 124 | 78         | 78    |
| "           | 3          | "                 | "               | "      | 179.0             | 343 | 297        | 297   |
| "           | 4          | "                 | "               | "      | 220.0             | 279 | 233        | 233   |
| "           | 5          | "                 | "               | "      | 271.0             | 227 | 181        | 181   |
| "           | 6          | "                 | "               | "      | 360.0             | 171 | 125        | 125   |
| 13 Apr 1020 | 1          | 22.0 $^{\circ}$ c | 1 hr.           | 1024   | 334.0             | 184 | 138        | 138   |
| "           | 2          | "                 | "               | "      | 308.0             | 200 | 154        | 154   |
| "           | 3          | "                 | "               | "      | 142.3             | 431 | 385        | 385   |
| "           | 4          | "                 | "               | "      | 159.8             | 385 | 339        | 339   |
| "           | 5          | "                 | "               | "      | 181.7             | 338 | 292        | 292   |
| "           | 6          | "                 | "               | "      | 236.5             | 260 | 214        | 214   |
| 13 Apr 1600 | 1          | 23.0 $^{\circ}$ c | 6 hr.           | 1024   | 102.5             | 600 | 554        | 570   |
| "           | 2          | "                 | "               | "      | 104.0             | 591 | 545        | 561   |
| "           | 3          | "                 | "               | "      | 65.2              | 941 | 895        | 921   |
| "           | 4          | "                 | "               | "      | 86.7              | 709 | 663        | 682   |
| "           | 5          | "                 | "               | "      | 109.0             | 564 | 518        | 534   |
| "           | 6          | "                 | "               | "      | 121.0             | 507 | 461        | 475   |



SERIES #6

Determination of Concentration

| Date & Time | Amount of Solution | Counts | Time      | CPM  |                 | Activity         | Activity Corrected For Decay |
|-------------|--------------------|--------|-----------|------|-----------------|------------------|------------------------------|
|             |                    |        |           | CPM  | less background |                  |                              |
| 13 Apr 1600 | .108ml             | 4096   | 88.6 sec  | 2766 | 2720            | .0880 $\mu$ c/ml | .0880 $\mu$ c/ml             |
| 15 Apr 1300 | .106ml             | 4096   | 108.0 sec | 2275 | 2236            | .0736 $\mu$ c/ml | .0876 $\mu$ c/ml             |

Test Data

| Date & Time | Planchet # | Temp.               | Total Immersion |  | Counts | Time     | CPM  | CPM Corrected for |       |
|-------------|------------|---------------------|-----------------|--|--------|----------|------|-------------------|-------|
|             |            |                     | Time            |  |        |          |      | Background        | Decay |
| 13 Apr 1600 | 1          | 24.0 <sup>0</sup> c | 5 min.          |  | 1024   | 126.5sec | 486  | 440               | 440   |
| "           | 2          | "                   | "               |  | "      | 107.0    | 575  | 529               | 529   |
| "           | 3          | "                   | "               |  | "      | 96.3     | 639  | 593               | 593   |
| "           | 4          | "                   | "               |  | "      | 129.0    | 476  | 430               | 430   |
| "           | 5          | "                   | "               |  | "      | 117.4    | 524  | 478               | 478   |
| "           | 6          | "                   | "               |  | "      | 126.8    | 486  | 440               | 440   |
| 13 Apr 1615 | 1          | 24.0 <sup>0</sup> c | 10 min.         |  | 1024   | 85.5     | 720  | 674               | 674   |
| "           | 2          | "                   | "               |  | "      | 74.0     | 831  | 785               | 785   |
| "           | 3          | "                   | "               |  | "      | 73.0     | 842  | 796               | 796   |
| "           | 4          | "                   | "               |  | "      | 81.8     | 752  | 706               | 706   |
| "           | 5          | "                   | "               |  | "      | 80.2     | 766  | 720               | 720   |
| "           | 6          | "                   | "               |  | "      | 83.4     | 739  | 693               | 693   |
| 14 Apr 0900 | 1          | 23.0 <sup>0</sup> c | 20 min.         |  | 1024   | 68.0     | 904  | 848               | 910   |
| "           | 2          | "                   | "               |  | "      | 60.2     | 1020 | 974               | 1031  |
| "           | 3          | "                   | "               |  | "      | 58.3     | 1055 | 1009              | 1070  |
| "           | 4          | "                   | "               |  | "      | 76.7     | 801  | 755               | 800   |
| "           | 5          | "                   | "               |  | "      | 68.3     | 900  | 854               | 905   |
| "           | 6          | "                   | "               |  | "      | 72.5     | 848  | 802               | 850   |
| 14 Apr 0920 | 1          | 23.0 <sup>0</sup> c | 30 min.         |  | 2048   | 126.0    | 976  | 930               | 986   |
| "           | 2          | "                   | "               |  | "      | 108.0    | 1140 | 1094              | 1160  |
| "           | 3          | "                   | "               |  | "      | 112.8    | 1091 | 1045              | 1108  |
| "           | 4          | "                   | "               |  | "      | 133.4    | 921  | 875               | 927   |
| "           | 5          | "                   | "               |  | "      | 123.5    | 996  | 950               | 1007  |
| "           | 6          | "                   | "               |  | "      | 133.2    | 924  | 878               | 931   |
| 14 Apr 1000 | 1          | 23.0 <sup>0</sup> c | 1 hr.           |  | 2048   | 107.0    | 1150 | 1104              | 1181  |
| "           | 2          | "                   | "               |  | "      | 95.0     | 1295 | 1249              | 1337  |
| "           | 3          | "                   | "               |  | "      | 97.8     | 1259 | 1213              | 1300  |
| "           | 4          | "                   | "               |  | "      | 114.3    | 1076 | 1030              | 1101  |
| "           | 5          | "                   | "               |  | "      | 105.7    | 1165 | 1119              | 1198  |
| "           | 6          | "                   | "               |  | "      | 116.0    | 1061 | 1015              | 1087  |
| 14 Apr 1100 | 1          | 23.0 <sup>0</sup> c | 2 hr.           |  | 2048   | 95.0     | 1295 | 1249              | 1337  |
| "           | 2          | "                   | "               |  | "      | 80.0     | 1540 | 1494              | 1600  |
| "           | 3          | "                   | "               |  | "      | 87.9     | 1400 | 1354              | 1450  |
| "           | 4          | "                   | "               |  | "      | 95.0     | 1295 | 1249              | 1337  |
| "           | 5          | "                   | "               |  | "      | 89.3     | 1380 | 1334              | 1429  |
| "           | 6          | "                   | "               |  | "      | 98.2     | 1252 | 1206              | 1290  |



|             |            |        |  | Total<br>Immersion |        |      |      |                                 |       |
|-------------|------------|--------|--|--------------------|--------|------|------|---------------------------------|-------|
| Date & Time | Planchet # | Temp.  |  | Time               | Counts | Time | CPM  | CPM Corrected for<br>Background | Decay |
| 14 Apr 1530 | 1          | 24.0°C |  | 6.5 hr.            | 2048   | 78.6 | 1565 | 1519                            | 1652  |
| "           | 2          | "      |  | "                  | "      | 60.0 | 2048 | 2002                            | 2225  |
| "           | 3          | "      |  | "                  | "      | 76.2 | 1612 | 1566                            | 1708  |
| "           | 4          | "      |  | "                  | "      | 84.0 | 1465 | 1419                            | 1545  |
| "           | 5          | "      |  | "                  | "      | 69.5 | 1770 | 1724                            | 1880  |
| "           | 6          | "      |  | "                  | "      | 58.5 | 2100 | 2054                            | 2240  |
| 15 Apr 1230 | 1          | 23.5°C |  | 27.25 hr.          | 2048   | 63.3 | 1945 | 1906                            | 2240  |
| "           | 2          | "      |  | "                  | "      | 49.8 | 2465 | 2426                            | 2850  |
| "           | 3          | "      |  | "                  | "      | 63.0 | 1954 | 1915                            | 2245  |
| "           | 4          | "      |  | "                  | "      | 64.0 | 1921 | 1882                            | 2215  |
| "           | 5          | "      |  | "                  | "      | 53.0 | 2320 | 2281                            | 2680  |
| "           | 6          | "      |  | "                  | "      | 26.0 | 4730 | 4691                            | 5500  |













MAR 9  
APR 6

BINDERY  
RECAT  
DISPLAY

25301

Thesis  
L99

Lynn

A study of the effect  
of variations of concen-  
tration and surface treat-  
ment on adsorption in a  
metallic copper-iodide  
ion system.

APR 6

BINDERY  
DISPLAY

25301

Thesis  
L99

Lynn

A study of the effect of varia-  
tions of concentration and surface  
treatment on adsorption in a me-  
tallic copper-iodide ion system.

thesL99

A study of the effect of variations of c



3 2768 002 12444 8

DUDLEY KNOX LIBRARY